Karlsruhe Institute of Technology

IAM
Institute for Applied Materials

Formation and development of nanoclusters in ODS steels and their influence on mechanical properties

S. Seils, D. Schliephake, A. Kauffmann, J. N. Wagner, M. Heilmaier

APT&M 2016 - Gyeongju

Institute for Applied Materials IAM-WK

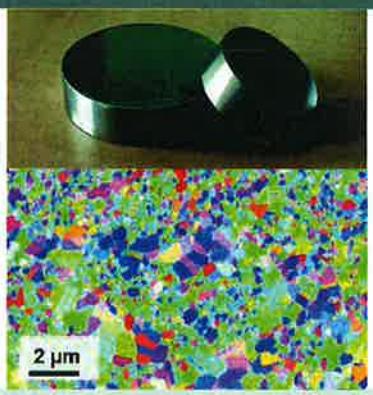

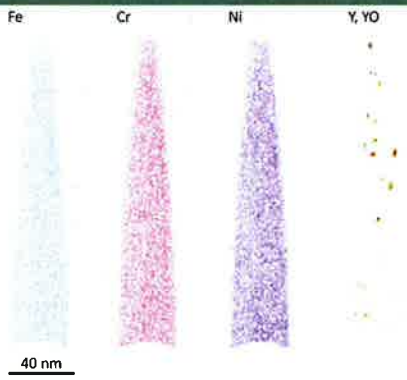

Deutsche Forschungsgemeinschaft DFG

HELMHOLTZ ASSOCIATION

KNMF Karlsruhe NANO MICRO Facility

KIT – The Research University in the Helmholtz Association

www.kit.edu

Motivation

ODS steels

- Nanoclusters
- Ultrafine-grained
- Radiation resistance
- Corrosion resistance
- Creep resistance

➢ How are the mechanical properties influenced by the microstructure?

- Expections
  - High thermal stability of Y-Ti-O particles
  - Pinning of grain boundaries by particles
  - Little grain growth

Materials

- Analysis of ferritic and austenitic ODS steels
- Improved high temperature properties of austenitic (fcc) ODS steel expected

In wt. %	Fe	Cr	Ni	Ti	Y_2O_3
FNC 14	Bal.	14		0.4	0.25
ANC 25/20	Bal.	25	20	0.4	0.25

- Decreasing Y_2O_3 particle size by titanium additions
- Formation of Y-Ti-O-containing nanoclusters (~ 4 nm)

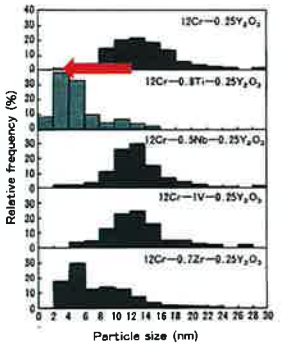

S. Ukai et al., J. Nucl. Mater. 307 (2002)

Processing

Zoz Simoloyer CM01
www.zoz-gmbh.de

Retsch PM400
www.retsch.de

- Cylinders with very low porosity
- Diameter between 20 and 40 mm

Mechanical Alloying

- Attritor or planetary ball mill
- Elemental powders + Y_2O_3
- Argon atmosphere

FAST

- Field Assisted Sintering Technique
- Pressure of 50 MPa
- 5 min at 1000 °C
- Fast heating and cooling rate (100 K/min)

- APT
- SEM / EBSD
- Annealing
- Compression tests

Atom probe measurements

- Tips produced by SEM/FIB
- LEAP 4000X HR by Cameca®

KNMF Karlsruhe Nano Micro Facility

FNC 14: mainly voltage mode

- detection rate: 0.3 %
- pulse rate: 200 kHz
- pulse fraction: 19 to 20 %
- temperature: 50 to 60 K

ANC 25/20: laser mode

- detection rate: 0.3 %
- pulse rate: 200 kHz
- pulse energy: 100 pJ
- temperature: 50 K

Reconstruction of a FNC 14 (FAST) tip

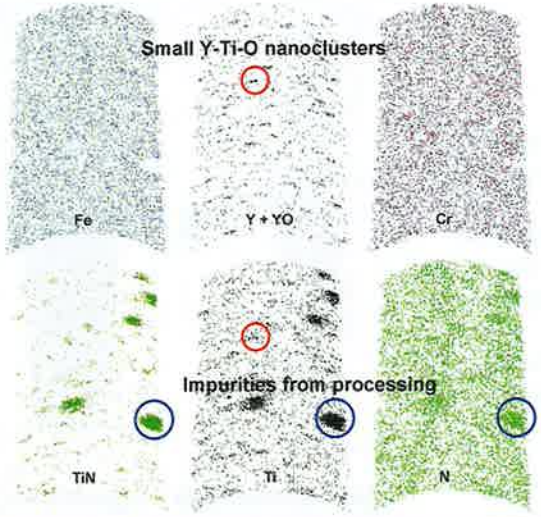

- 5 nm thick, 2-dimensional longitudinal section of the reconstruction
- Proof of cluster formation in FNC 14
- Identification of clusters with maximum separation method

Comparison of ANC 25/20 and FNC 14

ANC 25/20 (FAST)
- Cluster size: 4.9 nm
- Number density: $1.2 \cdot 10^{23}$ m^{-3}

FNC 14
- Similar volume fraction
- Smaller clusters
- Higher number density

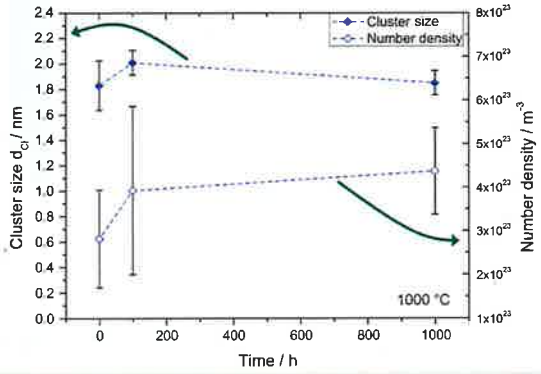

Composition of nanoclusters

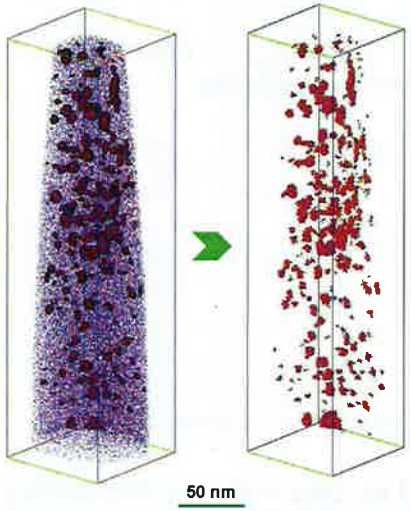

- Removal of matrix
- Modification of mass spectrum
- Decomposition of peaks

- Fe content artificially set to 0
- Cr (and Ni) content reduced proportionally

➢ Average composition of all identified nanoclusters

Composition of nanoclusters

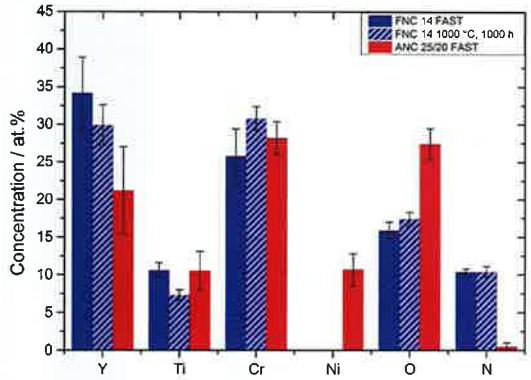

- No significant changes in **FNC 14** during annealing
- N seems to substitute O in **FNC 14**
- Ni seems to substitute Y in **ANC 25/20**

➢ Ratio of (Y,Ti,Cr,Ni) to (O,N) is around 3:1 in both alloys

Grain size

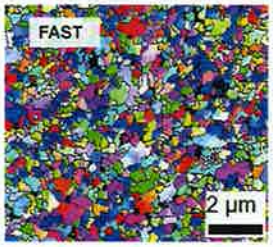

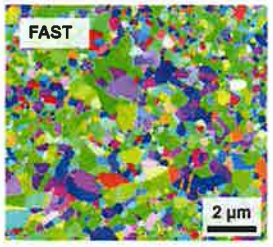

- Determination of grain size
- Orientation mappings from EBSD measurements
- Area weighted averaging

FNC 14 **ANC 25/20**

- Comparable grain size of all ODS steels after consolidation (between 0.4 and 0.5 µm)
- No grain growth even after 1000 h at 1000 °C
- Nanoclusters effectively pin grain boundaries and prevent grain growth

- No thermally induced changes in microstructure up to 1000 °C!

Mechanical properties – Compression tests

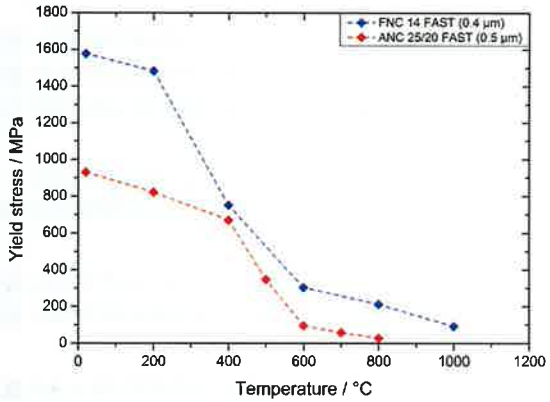



- Compression tests between room temp. and 1000 °C
- Constant strain rate: 10^{-4} s^{-1}

- Strength of **FNC 14** > **ANC 25/20** at all temperatures
- Influence of smaller clusters and higher amount of clusters
- Drop of strength for **ANC 25/20** at higher temperature

Modeling of strength

$$\sigma_{ys} = \sigma_0 + \sigma_{HP} + \sigma_{OW} + \sigma_{ss} \qquad \sigma_{HP} = \frac{k_{HP}}{\sqrt{d}} \qquad \sigma_{OW} = \frac{MGb}{d_p}\sqrt{\frac{6f}{\pi}}$$

Hall-Petch strengthening Orowan strengthening

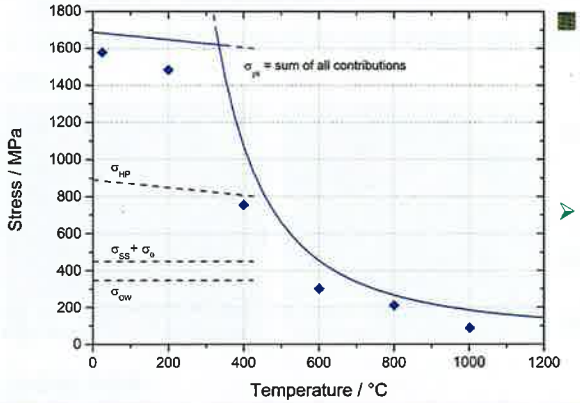

- Calculation of strengthening contributions in the low temperature range
- ➢ Calculated strength can depict results from compression tests very well.

Summary

- Production and analysis of ferritic and austenitic ODS steels
- APT for characterization of nanoclusters

- Large number of nanoclusters (< 5 nm) in both steels
- Ratio of Y, Ti, Cr(, Ni) to O (and N) was 3:1

- Nanoclusters and grain size (around 0.5 µm) stable during long-term annealing at 1000 °C

- Strength of **FNC 14** higher at all temperatures
- Drop of strength at higher temperature for **ANC 25/20**
- Calculation of strengthening contributions possible

Thank you very much for your attention!